

AD-A176 237

SOLID STATE BATTERIES(U) MINNESOTA UNIV MINNEAPOLIS
DEPT OF CHEMICAL ENGINEERING AND MATERIALS SCIENCE
M 2 MUNSHI ET AL JAN 87 N00014-85-K-0634

1/1

UNCLASSIFIED

F/G 10/3

NL





AD-A176 237

12

OFFICE OF NAVAL RESEARCH

Contract N00014-85-K-0634

R & T Code 413d019---01
Replaces Old
Task # 627-850

TECHNICAL REPORT NO. 1

Solid State Batteries

by

M. Z. A. Munshi and Boone B. Owens
Department of Chemical Engineering and Materials Science
University of Minnesota
Minneapolis, MN 55455

To be Published in

Proceedings of the Symposium on Electrochemistry and
Solid-State Science Education at the Graduate and Undergraduate Level

169th Meeting of the Electrochemistry Society
Boston, Mass.
May, 1986

Reproduction in whole or in part is permitted for any
purpose of the United States Government

This document has been approved for public release
and sale; its distribution is unlimited

DTIC FILE COPY

DTIC
ELECTE
JAN 29 1987
S D
E

87 1 28 030

REPORT DOCUMENTATION PAGE

1a. REPORT SECURITY CLASSIFICATION Unclassified		1b. RESTRICTIVE MARKINGS	
2a. SECURITY CLASSIFICATION AUTHORITY		3. DISTRIBUTION / AVAILABILITY OF REPORT Unclassified/Unlimited	
2b. DECLASSIFICATION / DOWNGRADING SCHEDULE			
4. PERFORMING ORGANIZATION REPORT NUMBER(S) ONR Technical Report #1		5. MONITORING ORGANIZATION REPORT NUMBER(S)	
6a. NAME OF PERFORMING ORGANIZATION Corrosion Research Center	6b. OFFICE SYMBOL (If applicable)	7a. NAME OF MONITORING ORGANIZATION Office of Naval Research, Resident Rep.	
6c. ADDRESS (City, State, and ZIP Code) University of Minnesota Minneapolis, MN 55455		7b. ADDRESS (City, State, and ZIP Code) Federal Building, Room 286 536 South Clark Street Chicago, IL 60605-1588	
8a. NAME OF FUNDING / SPONSORING ORGANIZATION Office of Naval Research	8b. OFFICE SYMBOL (If applicable) Code 1113	9. PROCUREMENT INSTRUMENT IDENTIFICATION NUMBER Contract No. N00014-85-K-0634	
8c. ADDRESS (City, State, and ZIP Code) 800 North Quincey Street Arlington, VA 22217-5000		10. SOURCE OF FUNDING NUMBERS	
		PROGRAM ELEMENT NO:	PROJECT NO.
		TASK NO.	WORK UNIT ACCESSION NO.
11. TITLE (Include Security Classification) Solid State Batteries			
12. PERSONAL AUTHOR(S) M.Z.A. Munshi and B.B. Owens			
13a. TYPE OF REPORT Technical	13b. TIME COVERED FROM 7/15/85 TO 12/30/86	14. DATE OF REPORT (Year, Month, Day) January 1987	15. PAGE COUNT 14 pages
16. SUPPLEMENTARY NOTATION Presented at 169th National Meeting of the Electrochemical Society, May 1986			
17. COSATI CODES		18. SUBJECT TERMS (Continue on reverse if necessary and identify by block number)	
FIELD	GROUP	SUB-GROUP	
19. ABSTRACT (Continue on reverse if necessary and identify by block number) The all solid state battery has been an idealized technological goal because of the assumption that the problems of batteries containing liquid phases are, at least in part, due to the fluid properties which can lead to high rates of self discharge, leakage of electrolyte through battery seals, and poor performance at both extremes of temperatures due to phase transitions. The major problem in developing useful solid state batteries has been to identify solid state ionically conducting materials with adequate conductivity to serve as the battery electrolyte. Recent work on new glasses and new polymer electrolytes have stimulated this field of investigation.			
20. DISTRIBUTION / AVAILABILITY OF ABSTRACT <input checked="" type="checkbox"/> UNCLASSIFIED/UNLIMITED <input type="checkbox"/> SAME AS RPT <input type="checkbox"/> OTIC USERS		21. ABSTRACT SECURITY CLASSIFICATION Unclassified	
22a. NAME OF RESPONSIBLE INDIVIDUAL Boone B. Owens		22b. TELEPHONE (Include Area Code) (612) 625-1332	22c. OFFICE SYMBOL

A

SOLID STATE BATTERIES

M. Z. A. Munshi and B. B. Owens

Department of Chemical Engineering & Materials Science
Corrosion Research Center
University of Minnesota

ABSTRACT

The all solid state battery has been an idealized technological goal because of the assumption that the problems of batteries containing liquid phases are at least in part due to the fluid properties which can lead to high rates of self discharge, leakage of electrolyte through battery seals, and poor performance at both extremes of temperature due to phase transitions. The major problem in developing useful solid state batteries has been to identify solid state ionically conducting materials with adequate conductivity to serve as the battery electrolyte. Recent work on new glasses and new polymer electrolytes have stimulated this field of investigation.

1. INTRODUCTION

Batteries have been successfully used as the most convenient portable form of stored electricity. In spite of the extensive investigations on batteries during the past century, there continues to be a need for further improvements in these devices. One of the areas of research has been in the application of solid state electrolytes to solid state batteries. In common with most battery systems the solid state batteries have solid electrodes. The distinction is that whereas the majority of batteries utilize a liquid electrolyte, the solid state battery incorporates an ionically conducting solid electrolyte based on ceramics, glasses, polymers or just simple ionic salts. The major advantages and disadvantages of solid electrolyte cells are summarized in Table 1.

One of the major problems in this field is the absence of solid electrolytes that exhibit adequately high ionic conductivities for appropriate ionic species. Some solid electrolyte batteries have been designed for operation at elevated temperatures where the electrical conductivity permits reasonable power levels. The greater interest is for solid state batteries that would be operable at normal ambient temperatures and in this area the materials problems remain challenging. A large number of silver ion conducting solid electrolytes have been reported (1) in which the conductivities are equivalent to those of aqueous solutions. The batteries developed around these electrolytes must incorporate silver electrodes and are inherently limited by the thermodynamic properties of the electrolyte to low energy density devices.

For	
&I	<input checked="" type="checkbox"/>
ed	<input type="checkbox"/>
ation	
ion/	

Availability Codes

Dist Avail and/or Special

A-1



There is a greater interest in alkali ion conducting solid state batteries that would have more energetic anodes and consequently higher levels of energy density. The last decade has witnessed the emergence of new batteries based on various lithium anode systems with significantly increased energy densities. However, these have been restricted to primary systems. The major areas of concern associated with primary batteries have been related to the presence of the liquid electrolyte phase. These include problems with cell leakage, internal self-discharge, case corrosion, drying out of the cell, loss of conductivity due to phase transitions at the extremes of temperatures, inability to withstand high levels of shock and severe restrictions on the capability for useful discharge at very low temperatures. The major interest in developing an all-solid-state battery with a solid electrolyte was to minimize these problems and design an active primary battery that was capable of storage or operation for up to ten years at uncontrolled temperatures ranging from -55° up to 70°C . In spite of extensive investigations on lithium solid state batteries, the major application for primary cells has been as a power source for cardiac pacemakers operating at low power levels ($100\text{ }\mu\text{W}$) and in a 37°C isothermal environment.

Lithium ion conducting solid electrolytes have received considerable attention and materials based on ceramics, glass compositions, ionic crystalline materials and polymeric materials have all been reported (4-8). Most recently, glasses and polymers have been designed into solid state batteries (9). The electrolytes are still fairly resistive, as shown in Table 2. Reasonable impedance batteries have resulted by designing cells with very thin electrolyte layers. The rechargeable lithium battery is not yet commercially available in consumer products, although primary cells have been sold for the past ten years. This difference arises in part from technical difficulties with liquid electrolyte systems and from a safety concept. A very high energy secondary rechargeable lithium battery is an attractive proposition, but the consumer market would be reluctant to accept a possibly unsafe product. A new family of cathode materials now being used for battery construction involves fast ionic transport (10). They are known as solid solution electrodes. The best solid solution electrode materials utilizing liquid electrolytes are conductors of lithium ions. A number of attempts have been made to develop solid state secondary lithium cells based on intercalation compounds such as TiS_2 or V_6O_{13} as the reversible cathode.

2. Battery Design

The lithium solid state batteries have received the most attention and it is possible to differentiate them in terms of the method in which their electrolyte element is formed. Table 3 also compares the properties of the silver-iodine solid state battery with three

lithium solid state batteries. As indicated, the silver-iodine battery utilizes a silver ion conducting electrolyte with resistances ranging from 3 to 100 ($\Omega\cdot\text{cm}$). However the low energy density as well as the cost of materials and manufacturing processes restricted the commercial application of this battery system. Three of the batteries in Table 3 are fabricated with discrete layers of the solid electrolyte formed from powdered materials. The Li/LiI/I₂(2VP) system does not involve discrete layers of electrolyte but instead the electrolyte forms in-situ by the direct chemical reaction between the electrode materials. This advantage of forming a resistive electrolyte in a very thin film minimizes the overall effect on battery impedance besides providing a simplified method of cell manufacture. In contrast, discrete layers require the formation of disks compacted at high pressures which is an added step in the battery production.

Several advantages have been cited for solid state batteries. However, there are also problems inherent with the design. These include:

- (1) low ionic conductivities of the electrolyte relative to that of the similar liquid electrolyte systems,
- (2) dimensional changes occurring during the discharge of a battery,
- (3) discharge product impedance
- (4) poor interfacial contact between the electrolyte and electrodes and current collector.

Another problem in an all-solid-state lithium battery is the question of safety. If the application could cause melting of the lithium metal, then lithium alloys with much higher melting points should be investigated. These have thus far been restricted to Li-Al or Li-Si alloys. As pointed out by Taylor (11), "The performance penalty that you suffer when using these alloys is quite substantial. There may be problems with the manufacturability of the product. One distinct advantage of lithium is that you can bend it, twist it, roll it, form it into thin foils and shape it into whatever you want, but whenever you start to alloy it with different materials, I'm not sure all that is possible".

3. Li-Ion Conducting Material

In recent years the solid electrolyte research in many laboratories has been directed to lithium ion conducting materials with the main emphasis being placed on an all-solid-state lithium batteries. Some of the highest room temperature lithium ion conductivities have been found in glasses based on ternary compositions containing LiI, Li₂S and either B₂S₃, GeS₂, or P₂S₅. Values reported have been as high as $2 \times 10^{-3} (\Omega\cdot\text{cm})^{-1}$ at 25°C (6,7). The activation energy has

been reported as 0.30 eV with t_+ for the lithium cation as being close to 1. Cells were fabricated using these glasses as either pressed powders or vacuum deposited thin films, with Li or Li-Al anodes and various cathodes (12,13). The stability of the electrolyte with electrode materials was investigated by calorimetric measurements of the heat flow from electrode/electrolyte mixtures that were pelletized and stored at 37°C. Only one $\mu\omega$ was observed over a 6 month storage interval for the glass mixed individually with LiAl, Bi₂Pb₂O₅ or TiS₂. The performance of Li/Bi₄B₂O₉ cells was reported² for current densities of 150 $\mu\text{A}/\text{cm}^2$ at 110°C with an open-circuit cell voltage of 2V. These new glasses appear feasible for small low power cells and possibly higher power cells operating near 100°C. However the interfacial properties between electrodes and electrolyte appear to restrict the rate capability.

Single crystal lithium nitride has also shown higher ionic conductivity due to the highly mobile lithium vacancies in this material. The development of new preparative techniques related to hydrogen-doped Li₃N has led to conductivity values as high as $6 \times 10^{-3} (\Omega \cdot \text{cm})^{-1}$ (14). Polycrystalline material has been manufactured with good mechanical and electrical properties ($\sigma \approx 3 \times 10^{-3} (\Omega \cdot \text{cm})^{-1}$ at room temperature). The application of this material as an electrolyte in rechargeable batteries depends on the ability to fabricate thin ceramic films. However, because the decomposition potential is low, ($\sim 0.4\text{V}$) the stability and practical energy density of any cell may be severely limited.

4. Polymer Electrolytes

The work of Fenton et al. (15) showing high ionic conductivity on solid polymer electrolytes based on polyethylene oxides (PEO) doped with an alkali metal salt, followed by Armand's (16) proposal for the use of such polymer electrolytes in an all-solid-state electrochemical battery has stimulated the development activities for all-solid-state lithium batteries. The attractive mechanical properties of this material resulted in further investigations on ionically conducting polymers. Conductivity values of 10^{-4} to $10^{-3} (\Omega \cdot \text{cm})^{-1}$ at 100°-140°C for PEO doped with lithium salts such as lithium-trifluoromethane sulphonate (LiCF₃SO₃) show that about eight PEO per Li are required to give a high value for ionic conduction. Materials that are more dilute with respect to the salt content yield higher conductivities. However the material is too soft to be used at higher temperatures and a ratio of 8 or 9 PEO/Li is generally regarded as the optimum composition, representing a quasi-solid material.

Differential scanning calorimetry experiments have shown the presence of both crystalline and amorphous phases and the general view (17) is that the highest conductivity occurs in the amorphous phase. Complex impedance studies using lithium reversible electrodes suggest the lithium transport number is about 0.5, and efforts are

underway to increase this value in order to avoid limiting current effects.

Other polymer systems under current investigation include nylon-6, polyethylene imine, polyvinylidene fluoride, and polyethylene sulphide. The conductivities of some of these are shown in Table 4. A limited number of actual cell tests have been carried out on the above mentioned polymers and the only one with any published degree of success is the lithium salt doped polyethylene oxide.

5. Polymer Electrolyte Batteries

During the past decade, extensive research has been made in the development of cells employing polymeric electrolytes. The principal thrust has been in Europe and Canada. The aims of the Anglo-Danish and Canadian-French programme have been to develop a secondary rechargeable all-solid-state lithium battery for a variety of applications including vehicular traction application and this has resulted in the emergence of a polymer electrolyte-based system (Figure 1). In its simplest form, the anode consists of lithium metal or a lithium alloy and the cathode consists of a composite structure containing the electrolyte phase together with V_6O_{13} and acetylene black. The polymeric solid electrolyte is sandwiched between the two electrodes. By fabricating the individual cell components as thin films, to compensate for the low conductivity of the electrolyte, reasonable impedance batteries have resulted. Typical dimensions used are:

25 - 30 μm electrolyte

25 - 50 μm Li electrode

100 - 150 μm V_6O_{13} cathode

The operating temperature of the cell is 100 - 140°C and current densities of 0.1 - 1.5 mA/cm² with PEO-LiCF₃SO₃ electrolytes are reported to give energy efficiencies and specific powers of 70-80% and 100-300 W/dm³ respectively, (13,30). The initial open circuit voltage of the system is over 3V. Further extensive research is now underway in developing the polymer electrolyte materials for battery applications.

Conclusions

Although the primary lithium solid state batteries are used as power sources for very low power devices such as cardiac pacemakers and electronic memory circuits, the possibility of a high (or medium) power all-solid-state rechargeable system continues to stimulate interest worldwide. The recent new developments in polymer and glass based electrolytes for battery applications, operating at elevated

temperatures of 100-150°C, has opened up the possibility of practical high energy, high power cells. However considerable work must be done to establish feasibility of a scaled-up battery.

Acknowledgement

This work was supported in part by the Office of Naval Research.

REFERENCES

1. B. B. Owens, "Solid Electrolyte Batteries" in Adv. in Electrochemistry and Electrochemical Eng., (C. Tobias, Ed.) Vol. 8, Ch. 1, Wiley, New York (1971).
2. B. B. Owens, P. M. Skarstad and D. F. Unterekar, in Handbook of Batteries and Fuel Cells (D. Linden, ed.), McGraw-Hill Book Company, New York, 1984, p. 12-1.
3. B. B. Owens and B. Scrosati, Proceedings of the 9th International CODATA Conference, Jerusalem, Israel (P. Glaeser, ed.) June, 1984.
4. A. Levasseur, M. Menetrier and P. Hagenmuller, Advanced Batteries and Fuel Cells, Proceedings of 3rd Contractors Meeting, Talence, France, ERU 8660 En, (1983).
5. European Patent EP 84-623 A.
6. I. Kelly, J. R. Owen and B. C. H. Steele, "Mixed Polyether Lithium Ion Conductor" Abs. No. 3, presented at the 2nd International Meeting on Lithium Batteries, April 25-7, 1984, Paris.
7. J. P. Malugani, B. Fahys, R. Mercier, G. Robert, J. P. Duchange, S. Bandy, M. Broussely and J. P. Gabano, Solid State Ionics, 9-10, (1983), 659.
8. J. P. Gabano, "Applications of Glasses in All Solid State Batteries - A review" presented at NATO Workshop on Glass Materials, Canary Isle, 1984.
9. J. R. Akridge and H. Vourlis, Proc. of the 5th Intn'l. Conf. on Solid State Ionics, Lake Tahoe, Aug. 18-24 (1985) p. 1082.
10. B. C. Tofield, R. M. Dell and J. Jensen, "Advanced Batteries", Nature, Vol. 276, No. 5685, pp. 217-220 (1978).
11. H. Taylor, (Proc.) 2nd International Meeting on Lithium Batteries, Paris, 1984, Elsevier Sequoia S. A., 1985, p. 262.
12. A. Hooper and J. M. North, Solid State Ionics, 9-10 (1983), 1161.
13. J. M. North, T. L. Markin, A. Hooper and B. C. Tofield, "Solid State Rechargeable Lithium Batteries," Abs. No. 19 presented at the 2nd International Meeting on Lithium Batteries, April 25-27, (1984) Paris.
14. J. Jensen, in Progress in Solid Electrolytes ed. by T. A. Wheat, A. Ahmad, and A. K. Kuriakose, p. 473, (1983).
15. B. E. Fenton, J. M. Parker and P. V. Wright, Polymer, 14 (1973), 589.

THE ELECTROCHEMICAL SOCIETY, INC.
CAMERA READY COPY TYPING FORM

16. M. Armand, J. M. Chabagno and M. Duclot, in: "Fast Ion Transport in Solids, eds. P. Vashista, J. N. Mundy and G. K. Shenoy (North Holland, Amsterdam, (1979), p. 131.
17. C. D. Robitaille and D. Fauteux, J. Electrochem. Soc. Vol. 133, 2 (1986), 315.
18. C. R. Martin, T. A. Rhoades and J. A. Ferguson, Anal. Chem., 54 1641, (1982).
19. M. B. Armand, "Solid State Batteries" (ed. C. A. C. Sequeira and A. Hooper), p. 63 (1985) pub. Nijhoff.
20. G. Feuillade and P. H. Perche, J. Appl. Electrochem., 5, 63, (1975).
21. M. B. Armand, Lithium, non-aqueous batteries electrochemistry, The Electrochem. Soc. ed. Pennington, 80-7, 261, (1980).
22. K. Tsunemi, H. Ohno and E. Tsuchida, Electrochim. Acta, 28, 6, 833, (1983).
23. J. M. Chabagno, Thesis-U of Grenoble, (1980).
24. J. R. MacCallum, M. J. Smith and C. A. Vincent, Solid State Ionics, 11, 4, 307, (1984).
25. M. B. Armand, J. M. Chabagno and M. J. Duclot, Fast Ion Transport in Solids, P. Vashista ed. North Holland (N.Y.), 131, (1979).
26. R. D. Armstrong and M. D. Clark, Electrochim. Acta., 29-10, 1443, (1984).
27. R. Dupon, B. L. Papke, M. A. Ratner and D. F. Shriver, J. Electrochem. Soc., 131-3, 586, (1984).
28. D. F. Shriver, B. L. Papke, M. A. Ratner, R. Dupon, T. Wong and M. Brodroing, Solid State Ionics, 5, 83, (1981).
29. M. B. Armand, Solid State Ionics, 9 and 10, 745, (1983).
30. Gauthier, D. Fauteux, G. Vassort, A. Belanger, M. Duval, P. Ricoux, J. M. Chabagno, D. Muller, P. Rigaud, M. B. Armand and D. Deroo, J. Electrochem. Soc., 132, 6 (1985) 1333.

Table 1: MAJOR ADVANTAGES AND DISADVANTAGES OF LITHIUM SOLID-ELECTROLYTE CELLS (REF. 2)

Excellent storage stability-- shelf life of 10 y or better	Low current drains (micro- amperes)
High energy densities	Power output reduced at low temperatures
Hermetically sealed-no gassing or leakage	Care must be exercised to prevent shorting or shunting of cell (which could be a relatively high drain on cell)
Wide operating temperature range, up to 200°C	
Shock- and vibration-resistant	

Table 2: Resistivity R of Electrolytes for Solid State Batteries at Ambient Temperature. (Ref. 3)

Electrolyte	Log of R
-Li I	6 to 7
-Li I-Dispersed Phase e.g. LiI(Al ₂ O ₃)	4 to 5
-Li Polymers e.g. PEO ^A , LiClO ₄	4 to 5
-Li Glasses e.g. Li ₂ S, P ₂ S ₅ , LiI	3 to 4
-Li-β-Alumina	3 to 4
-Li ₃ N	3 to 4
-Ag or Cu Electrolyte Salts e.g. RbAg ₄ I ₅ , Rb ₄ Cu ₁₆ I ₇ Cl ₁₃ , Ag ₃ SI	1 to 2

^APEO is Polyethylene oxide.

Table 3: Characteristics of Solid-Electrolyte Cells (Ref. 1)

System	Cell voltage, V	Energy density at 1-Y rate	
		Wh/L	Wh/kg
Ag/RbAg ₄ I ₅ /Me ₄ NI ₅ , C	0.66	40-80	15-25
Li/LiI(Al ₂ O ₃)/PbI ₂ , PbS, Pb	1.9	300-600	75-150
Li/LiI/I ₂ (P2VP)	2.8	350-700	120-200
Li/LiI(SiO ₂)/Me ₄ NI ₅	2.75	400	125

Table 4: Conductivity of Polymer Electrolytes

Solid Electrolyte	$\sigma(\Omega\text{cm})^{-1}/T^{\circ}\text{C}$	Ref.
(PEO) _x LiCF ₃ SO ₃ (monomer-salt = 8:1)	10^{-3} - $10^{-4}/100$ - 140°C	(14)
Nafion ^R Li ⁺ PC	$2 \times 10^{-3}/\text{R.T.}$	(18)
Ion exchange membranes with attached ionophoretic groups	10^{-12} - $10^{-15}/\text{R.T.}$	(19)
Viton ^R cross-linked with diamine and gelled with 1M PC-LiClO ₄	$6 \times 10^{-3}/100$	(19)(20)(21)(22)
Poly(vinylidene fluoride) gelled with PC-LiClO ₄	$2 \times 10^{-3}/100^a$	(19)(20)(21)(22)
PEO-LiClO ₄ , 12:1	$2 \times 10^{-3}/100$	(23)
xlinked PEO-LiClO ₄ , 8:1	$6 \times 10^{-4}/100$	(24)
PEO-LiCF ₃ SO ₃ , 9:1	$2 \times 10^{-4}/100$	(25)
Polyethylene adipate LiCF ₃ SO ₃ , 4:1	$7 \times 10^{-5}/100$	(26)
Polyethylene succinate LiBF ₄ , 6:1	$5 \times 10^{-5}/100$	(27)
Polybis (methoxy-ethoxy-ethoxy phosphogene)-LiCFSO ₃ , 4:1	$7 \times 10^{-4}/100$	(28)
Poly(N-methyl aziridine) LiClO ₄ , 8:1	$10^{-5}/100$	(19)
PPO - LiI 8:1	$\sim 3 \times 10^{-4}/100$	(29)
PPO - LiCF ₃ SO ₃ , 9:1	$1.5 \times 10^{-4}/100$	(29)
a - extrapolated value		

PEO = polyethylene oxide

PC = propylene carbonate

PPO = polypropylene oxide

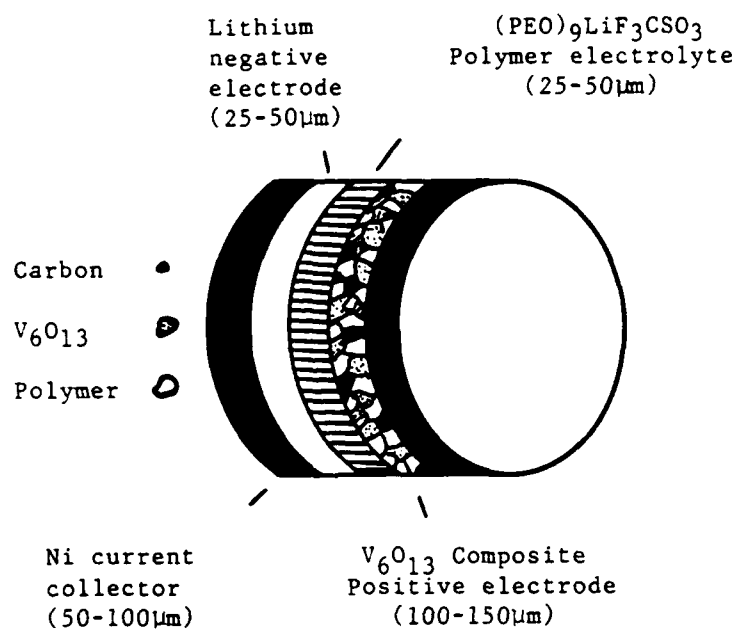


Figure 1: Solid-State Cell

THE ELECTROCHEMICAL SOCIETY, INC.
CAMER - READY COPY TYPING FORM

Key words:

batteries, lithium	- page 1
intercalation, design	- page 2
conductivity, glasses	- page 3
polymer, impedance	- page 4
salt, electrolyte	- page 5

TECHNICAL REPORT DISTRIBUTION LIST, GEN

	<u>No. Copies</u>		<u>No. Copies</u>
Office of Naval Research Attn: Code 1113 800 N. Quincy Street Arlington, Virginia 22217-5000	2	Dr. David Young Code 334 NORDA NSTL, Mississippi 39529	1
Dr. Bernard Douda Naval Weapons Support Center Code 50C Crane, Indiana 47522-5050	1	Naval Weapons Center Attn: Dr. Ron Atkins Chemistry Division China Lake, California 93555	1
Naval Civil Engineering Laboratory Attn: Dr. R. W. Drisko, Code L52 Port Hueneme, California 93401	1	Scientific Advisor Commandant of the Marine Corps Code RD-1 Washington, D.C. 20380	1
Defense Technical Information Center Building 5, Cameron Station Alexandria, Virginia 22314	12 high quality	U.S. Army Research Office Attn: CRD-AA-IP P.O. Box 12211 Research Triangle Park, NC 27709	1
DTNSRDC Attn: Dr. H. Singerman Applied Chemistry Division Annapolis, Maryland 21401	1	Mr. John Boyle Materials Branch Naval Ship Engineering Center Philadelphia, Pennsylvania 19112	1
Dr. William Tolles Superintendent Chemistry Division, Code 6100 Naval Research Laboratory Washington, D.C. 20375-5000	1	Naval Ocean Systems Center Attn: Dr. S. Yamamoto Marine Sciences Division San Diego, California 91232	1

END

2-87

DTIC